

Experimental evidence for the coupling of Li-motion and structural distortions in LiMnPO_4

Christian Rudisch,¹ Hans-Joachim Grafe,¹ Jochen Geck,¹ Sven Partzsch,¹
M. v. Zimmermann,² Nadja Wizent,^{1,3} Rüdiger Klingeler,³ and Bernd Büchner¹

¹*IFW Dresden, Leibniz Institute for Solid State and Materials Research, D-01171 Dresden, Germany*

²*Deutsches Elektronen-Synchrotron DESY, D-22603 Hamburg, Germany*

³*Kirchhoff-Institut für Physik, Universität Heidelberg, D-69120 Heidelberg, Germany*

(Dated: April 19, 2013)

We present a detailed ^7Li - and ^{31}P -NMR study on single crystalline LiMnPO_4 in the paramagnetic and antiferromagnetic phase (AFM, $T_N \sim 34$ K). This allows us to determine the spin directions in the field-induced spin-flop phase. In addition, the anisotropic dipolar hyperfine coupling tensor of the ^7Li - and ^{31}P -nuclei is also fully determined by orientation and temperature dependent NMR experiments and compared to the calculated values from crystal structure data. Deviations of the experimental values from the theoretical ones are discussed in terms of Mn disorder which is induced by Li-disorder. In fact, the disorder in the Mn-sublattice is directly revealed by our diffuse x-ray scattering data. The present results provide experimental evidence for the Li-diffusion strongly coupling to structural distortions within the MnPO_4 host, which is expected to significantly affect the Li-mobility as well as the performance of batteries based on this material.

PACS numbers: 76.60.-k, 75.25.+z, 75.50.Ee, 61.10.Nz

I. INTRODUCTION

Since the pioneering work of Padhi et al.¹ in 1997, the phospho-olivine materials are highly interesting for an application in rechargeable lithium batteries. LiMnPO_4 is a member of the olivine type lithium phosphate family and features several advantages regarding battery technology such as excellent chemical and thermal stability, non-toxicity in contrast to LiCoO_2 , and economic viability and availability of the raw materials²⁻⁴. Despite these clear advantages of LiMnPO_4 for battery applications, there are also reports about its poor electrochemical performance^{1,5-7}. The reasons for this currently remain unclear, but it has been found that LiMnPO_4 incorporated in carbon coated nanostructures provides a competitive next generation cathode material with a stable reversible capacity up to 145 mAh/g and a rather flat discharge voltage curve at 4.1 V^{8,9}.

Besides its relevance for battery applications LiMnPO_4 also exhibits interesting magnetic properties. More specifically, applying a magnetic field leads to a spin flop phase with a slight ferromagnetic canting, which could exhibit magnetoelectric effects¹⁰. In addition, in LiMPO_4 with $M = \text{Co}$ or Ni unusual ferrotoroidic domains have been discovered¹¹.

In this article we address the origin of the poor electrochemical performance of LiMnPO_4 as well as the possible magnetoelectric effect in this material. To this end, we performed full orientation and temperature dependent ^7Li and ^{31}P NMR experiments on a single crystal of LiMnPO_4 . This allowed us to determine the complete dipolar hyperfine coupling tensor $\hat{A}_{\text{dip}}$ which is compared to the calculated one from the positions of the atoms in the unit cell. Deviations of the experimentally obtained hyperfine coupling tensors from the calculated tensors

and an anomalous broadening of the resonance lines in the paramagnetic phase are discussed in terms of Mn disorder in the samples. The conclusions from NMR are corroborated by our diffuse x-ray diffraction (HE-XRD) experiments, which directly reveal the disorder in the Mn-sublattice. The NMR spectra in the AFM phase have been measured at 4.2 K, and the number of resonance lines agrees with the calculated spectra. Furthermore, the spectra allowed us to determine the spin directions in the spin-flop phase as well as the tilt of the spins due to the applied external magnetic field, which is important in order to assess the possible magnetoelectric effect in this material.

Our findings of Mn disorder in LiMnPO_4 provides firm experimental evidence that the movement of Li within LiMnPO_4 is strongly coupled to the lattice. Certainly, this affects also the mobility of the Li in LiMnPO_4 , and therefore the performance of this material as a battery. Interestingly, our results are perfectly consistent with a recent theoretical study which found a formation of a vacancy-polaron complex by a lithium vacancy and a corresponding hole-polaron at the fully lithiated limit owing to lattice distortion and Coulomb interaction between them⁵, and thereby explaining the poor electrochemical performance of LiMnPO_4 if non-carbon coated microstructures or single crystals are considered.

II. EXPERIMENTAL DETAILS

A. Sample preparation and characterization

The single crystal investigated in this work was grown at the IFW Dresden by the floating-zone method^{12,13}. A phase pure single crystalline grain of the approximate size of $2 \times 2 \times 4$ mm was cut out of the grown rod.

The phase purity was checked by x-ray diffraction measurement. The crystal structure of LiMnPO_4 shown in Fig. 1 belongs to the Pnma spacegroup. The Mn atoms are surrounded by distorted octahedra of oxygen atoms. The P atoms are tetrahedrally surrounded by oxygen atoms forming PO_4^{3-} groups¹⁴. There are four Li and four P positions which are crystallographically equivalent. The Mn ions are in a Mn^{2+} state resulting in a spin of $S = 5/2$ and an effective magnetic moment of $5.9 \mu_B$ ¹². The Mn magnetic moments align antiferromagnetically below $T_N \sim 34 \text{ K}$ ¹² along the a -axis¹⁵.

B. NMR and Hyperfine Coupling Tensor

Nuclear Magnetic Resonance (NMR) is an ideal tool to study both the Li diffusion process, which is important for application in lithium ion batteries, as well as the local magnetic properties. The Li diffusion process determines the mobility of the Li ions in a material and can be investigated by ^7Li -NMR linewidth and spin lattice relaxation measurements^{16,17}, while the magnetism can be probed by any nucleus in the material that is coupled to the magnetic ion. For both processes, the detailed knowledge of the hyperfine coupling tensor between the electron spin and the nuclear probes –here the nuclear spins of ^7Li and ^{31}P – is helpful.

All NMR experiments reported here are done at a constant field of $H_0 = 7.0494 \text{ T}$. For orientation dependent NMR measurements a probe with a single axis goniometer was used which allows to rotate the sample by a certain angle inside the magnet. The temperature dependent NMR measurements were done in a temperature range from 4.2 K up to 420 K . In the following, only the dipolar hyperfine coupling will be described in detail, since as we will see the other hyperfine couplings are either negligible (quadrupolar coupling, diamagnetic and orbital shift) or isotropic (Fermi contact from unpaired s -electrons on the ^{31}P).

The Hamiltonian describing the dipolar coupling of the nuclear spin to the Mn electronic spins is expressed by

$$\mathcal{H}_{\text{dip}} = \hbar \gamma_n B_{\text{dip}} = -\frac{\mu_0}{4\pi} \gamma_e \gamma_n \hbar^2 \sum_j \vec{I} \cdot \hat{A}_{\text{dip},j} \cdot \vec{S}_j^T. \quad (1)$$

Where B_{dip} represents the dipolar field of the electronic spin located at the Mn site. γ_n corresponds to the gyromagnetic ratio of the nuclei ^7Li and ^{31}P ($\gamma_{\text{Li}}=16.5461 \text{ MHz}$, $\gamma_{\text{P}}=17.2347 \text{ MHz}$). γ_e is the gyromagnetic ratio of the electron. The nuclear and j th electron spin are represented by $\vec{I}$ and $\vec{S}_j^T$ respectively. The anisotropic dipolar coupling between the nuclear and the electron spins is described by the dipolar hyperfine coupling tensor $\hat{A}_{\text{dip}}$ (see e.g.¹⁸). It has been calculated for the paramagnetic $\hat{A}_{\text{dip}}^{\text{para}}$ and AFM phase $\hat{A}_{\text{dip}}^{\text{AFM}}$ from the crystal structure data.

All electron spins within a sphere with a radius of $100 \text{ \AA}$ have been considered, leading to the same tensor elements A_{mn} of $\hat{A}_{\text{dip}}$ as reported by Mays et al.¹⁴.

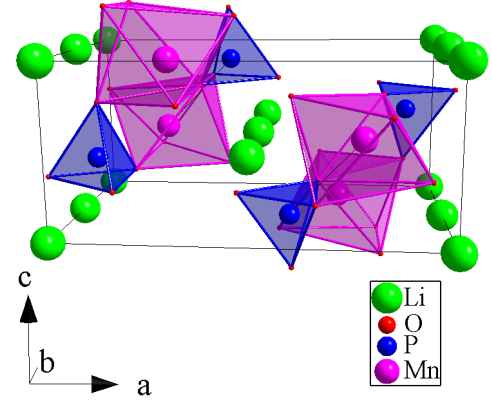


FIG. 1. Crystal structure of LiMnPO_4 . The crystallographic axes (a , b , and c) are along the edges of the unit cell. The slightly distorted MnO_6 octahedra (shaded in violet) share the oxygen anions with the PO_4 tetrahedra (shaded in blue).

The different positions in the crystal of the ^7Li and the ^{31}P naturally lead to different dipolar hyperfine coupling tensors $\hat{A}_{\text{dip,Li}}$ and $\hat{A}_{\text{dip,P}}$, respectively. Crystallographically, there are four equivalent ^7Li and ^{31}P sites in the unit cell. However, for each nucleus, the diagonal elements A_{mm} of $\hat{A}_{\text{dip}}$ are the same, whereas the off diagonal elements $A_{mn} (m \neq n)$ are different. Therefore, for both nuclei, single resonance lines are expected for $H_0 \parallel a, b$, and c , whereas the different off diagonal elements lead to a splitting of the resonance lines for angles off these high symmetry directions in the paramagnetic phase.

In the antiferromagnetically ordered state, $\hat{A}_{\text{dip,Li}}^{\text{AFM}}$ vanishes, i.e. no internal, dipolar field remains at the Li sites, leading to an unshifted single resonance line for the ^7Li . The calculation of $\hat{A}_{\text{dip,P}}^{\text{AFM}}$ leads to four magnetically inequivalent P sites in the AFM phase. Note that the diagonal elements of these P sites are different. Therefore, up to four ^{31}P -NMR lines are expected in the AFM phase. The calculated tensor elements of the paramagnetic and the AFM phase for ^7Li and ^{31}P nuclei are listed in Tab. I where a comparison of calculated and experimentally determined values is given.

C. X-ray diffraction experiments

Complementary structural information has been obtained by high-energy x-ray diffraction (HE-XRD) studies on the same single crystal. The experiments were performed at the beamline BW5 at the HASYLAB in Hamburg, using x-rays with photon energies of 100 keV . Due to the large penetration depths at this energy ($\sim 1 \text{ mm}$), surface effects have no influence on the detected signal, ensuring the detection of real bulk properties. We performed triple-axis diffraction in horizontal Laue geometry utilizing the (111) reflection of a Si/Ge-monochromator

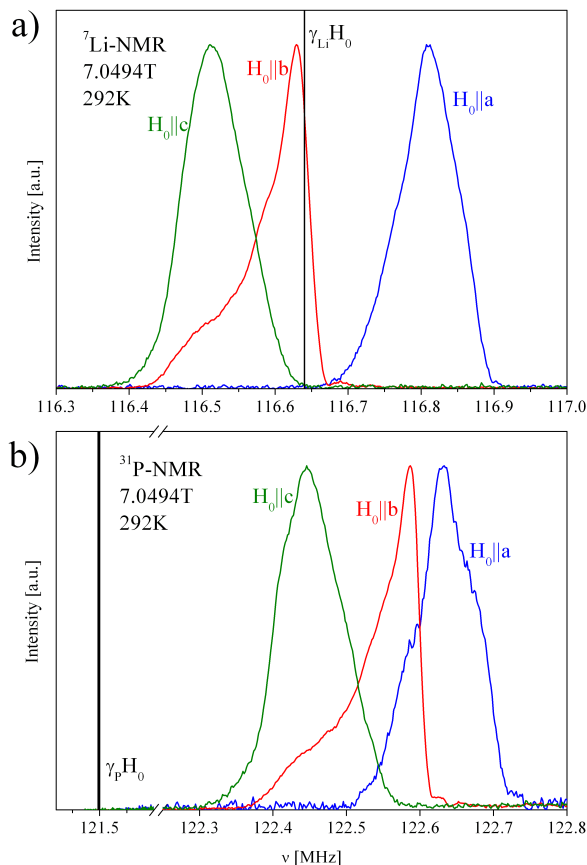


FIG. 2. (a) ${}^7\text{Li}$ -NMR spectra and (b) ${}^{31}\text{P}$ -NMR spectra for the orientations $H_0||a$, $H_0||b$ and $H_0||c$. The average linewidth is ~ 80 kHz. The ${}^7\text{Li}$ -NMR spectra in (a) exhibit a small shift around the resonance line of a bare nucleus ($\gamma_{\text{Li}}H_0$). The ${}^{31}\text{P}$ -NMR spectra in (b) are showing large shifts to higher resonance frequencies which can be due to the isotropic contact interaction, see text.

and Si/Ge-analyzer crystal.

III. RESULTS AND DISCUSSION

A. NMR spectra and temperature dependence

In Fig. 2 the ${}^7\text{Li}$ - and ${}^{31}\text{P}$ -NMR spectra are shown for $H_0||a$, $H_0||b$, and $H_0||c$ at 292 K. Due to the anisotropy of the dipolar hyperfine couplings $\hat{A}_{\text{dip,Li}}$ and $\hat{A}_{\text{dip,P}}$ the resonance frequency ν is different for the different orientations. The ${}^7\text{Li}$ -NMR spectra for all different orientations are spanning a frequency interval of 500 kHz at 292 K. This value agrees well with the full width of ${}^7\text{Li}$ -NMR spectra in LiMnPO_4 powder samples reported in¹⁹. The linewidth shows a linear field dependence (e.g. $\Delta\nu(7\text{T}) \sim 80$ kHz, whereas $\Delta\nu(3\text{T}) \sim 40$ kHz). This indicates a dipolar broadening, where each ${}^7\text{Li}$ (${}^{31}\text{P}$) nucleus sees a slightly different dipolar hyperfine field of

the Mn electronic spins. However, the asymmetric shape of the resonance lines (especially for $H_0||b$) differs much from the expected Gaussian shape of a resonance line in a single crystal, indicating a substantial amount of disorder in the sample. For this reason, we have calculated the Knight shift of the ${}^7\text{Li}$ and ${}^{31}\text{P}$ from the center of gravity of the resonance lines, and the width $\Delta\nu$ of the spectra has been determined by the square root of the second moment.

Furthermore, a comparison of the resonance lines in Fig. 2 shows that for the corresponding orientations the shape of ${}^7\text{Li}$ - and ${}^{31}\text{P}$ -NMR spectra are very similar. This indicates that the shape of the resonance lines of both nuclei must be affected by the same factor. If only the ${}^7\text{Li}$ is disordered in the crystal, this would not affect the ${}^{31}\text{P}$ resonance lines and vice versa.

A misalignment of the external field can be excluded, too, since the crystal was accurately oriented by making use of the angle dependence of the resonance frequencies of the ${}^7\text{Li}$ - and ${}^{31}\text{P}$ resonance lines (see Fig. 5, 6, and 7). A quadrupolar broadening or splitting of the ${}^7\text{Li}$ - spectra ($I = 3/2$) could also not be observed, indicating a very small electric field gradient at the Li site. Therefore, the anomalous shape of the resonance lines of both nuclei must originate either from a distribution of local moments of the Mn, i.e. a distribution of the valence of the Mn, or a distribution of the hyperfine coupling which can originate from a site disorder of the Mn. Since there are no indications for a distribution of the Mn valence¹², we conclude that there is substantial Mn site disorder. A detailed comparison of the calculated and experimental hyperfine coupling tensor elements in the following points into the same direction. Further investigations by diffusive x-ray scattering (see Chapter 4) corroborate the existence of Mn site disorder in LiMnPO_4 .

The temperature dependence of the resonance frequencies for ${}^7\text{Li}$ - and ${}^{31}\text{P}$, $\nu(T)$, is shown in Fig. 3 (a) and (b). In the paramagnetic phase, $\nu(T)$ can be described by

$$\nu(T) = \gamma_n H_0 (1 + A_{mm} \chi(T)). \quad (2)$$

where A_{mm} are the diagonal dipolar hyperfine coupling tensor elements for the corresponding orientations ($H_0||a$, $H_0||b$, $H_0||c$, $m=1, 2, 3$ respectively). The magnetic susceptibility is isotropic in the paramagnetic phase¹², and thus $\chi(T)$ is a scalar in Eqn. 2. From Clogston Jaccarino plots the diagonal elements A_{mm}^{exp} are obtained for the corresponding orientations (see Appendix Tab. I). Since A_{22} and A_{33} for ${}^7\text{Li}$ are negative, the resonance lines for $H||a$ and b shift to lower frequencies. For the ${}^{31}\text{P}$, there is an additional temperature dependent contact term (see Fig. 2 (b)) which leads to a positive shift of the resonance frequency for all three directions. The contact term is also responsible for the large deviation of the calculated and experimentally determined coupling constants in Tab. I. Further deviations may arise from the anomalous shape of the spectra due to the Mn disorder.

The temperature dependence of the square root of the second moment $\Delta\nu$ of the ${}^7\text{Li}$ and ${}^{31}\text{P}$ -NMR spectra

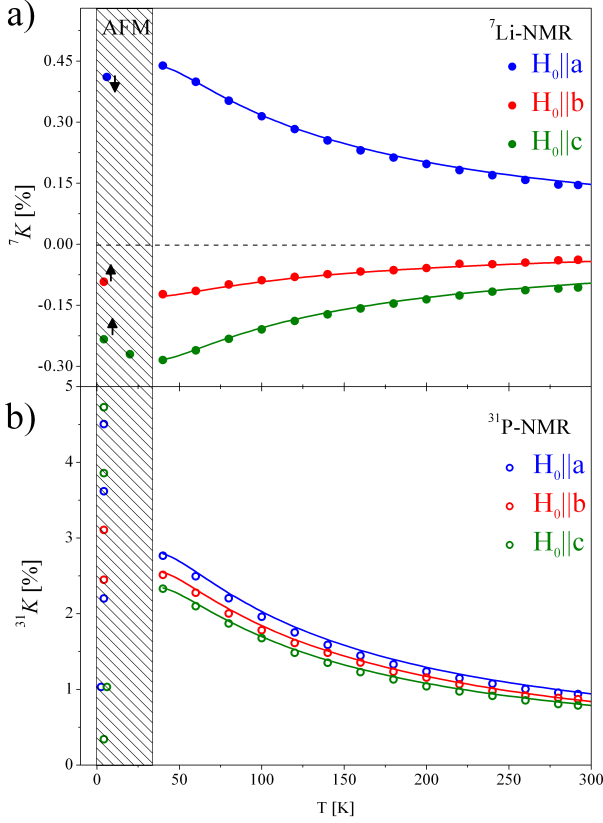


FIG. 3. Temperature dependence of the Knight shift (a) ${}^7\text{K}$ and (b) ${}^{31}\text{K}$ for the orientations $H_0||a$, $H_0||b$ and $H_0||c$ in the paramagnetic and AFM phase. The measured data are indicated by the dots. The solid lines correspond to the Knight shift which is calculated by $K = A_{mm}^{\text{exp}}\chi(T)$ with $m=1,2,3$ for $H_0||a$, $H_0||b$ and $H_0||c$, respectively. The diagonal tensor elements A_{mm}^{exp} are determined from fits of Clogston Jaccarino plots and listed in Tab. I. (a) The presence of the anisotropic dipolar coupling leads to positive and negative ${}^7\text{K}$ for corresponding orientation. In the AFM phase the single resonance line shifts towards ${}^7\text{K} = 0$ which is indicated by the arrows. (b) The superposition of the field caused by the contact term and the field of the dipolar coupling leads to a comparatively high ${}^{31}\text{K}$. In the AFM phase four resonance lines are observed for $H_0||a$ and $H_0||c$ and two for $H_0||b$.

is shown in Fig. 4. With decreasing temperature $\Delta\nu$ increases which is the expected behavior for magnetic broadening which scales with the susceptibility χ . For $H_0||c$ the spectra were measured up to 420 K (see Fig. 4). Above ~ 300 K, the second moment is almost constant yielding a value of $\Delta\nu \sim 80$ kHz. As can be seen in Fig. 4, $\Delta\nu$ of the ${}^{31}\text{P}$ -NMR spectra is slightly larger for the corresponding orientations than $\Delta\nu$ of the ${}^7\text{Li}$. The reason for this could be a distribution of the hyperfine fields transferred by the contact interaction which affects only the ${}^{31}\text{P}$, but not the ${}^7\text{Li}$. The effect of the contact interaction is isotropic, hence the ${}^{31}\text{P}$ -NMR spectra are broadened without additional features in the shape of the resonance line.

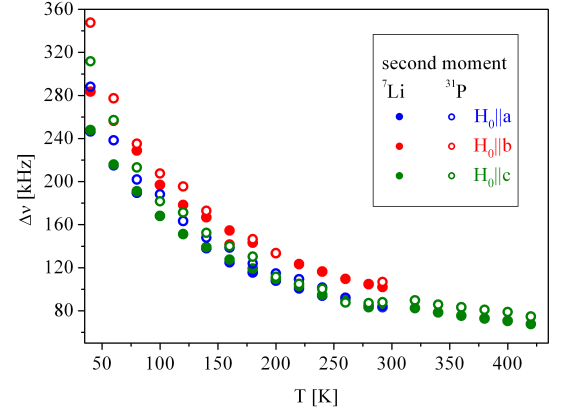


FIG. 4. Comparison of the temperature dependent second moment $\Delta\nu$ between ${}^7\text{Li}$ - and ${}^{31}\text{P}$ -NMR spectra. The second moment of the ${}^{31}\text{P}$ -spectra is almost always larger than the corresponding second moment of the ${}^7\text{Li}$ -spectra. This effect is predominantly related to a distribution of internal fields by the contact interaction on the P nuclei. For $H_0||c$ the spectra are measured up to 420 K, where the second moment remains almost constant at 80 kHz.

B. Angle-dependent NMR frequencies

The full experimental orientation dependence of ${}^7\text{Li}$ - and ${}^{31}\text{P}$ -NMR can be described consistently with the susceptibility data and the hyperfine coupling tensor $\hat{A}_{\text{dip}}^{\text{para}}$.

The angle-dependent NMR data was obtained by rotating the crystal around the crystal axes from $H_0||c$ to $H_0||a$, from $H_0||b$ to $H_0||a$, and from $H_0||b$ to $H_0||c$ at 292 K. The angle dependence at this temperature can be described by

$$\nu(\phi, \theta) = \gamma_n H_0 \left(1 + \begin{pmatrix} \cos \phi \sin \theta \\ \sin \phi \sin \theta \\ \cos \theta \end{pmatrix} \hat{A}_{\text{dip}}^{\text{para}} \begin{pmatrix} \cos \phi \sin \theta \\ \sin \phi \sin \theta \\ \cos \theta \end{pmatrix} \right) \chi(292\text{K}) \quad (3)$$

where the orientation of the crystal structure in the external field is expressed by the unit vectors given in spherical coordinates. The experimental and calculated data according to Eqn. 3 are shown in Fig. 5 to Fig. 7. For the calculated curves the corresponding experimental diagonal elements and the calculated off diagonal elements are used. The splitting of the resonance lines for angles off the high symmetry directions is caused by the different magnetic ${}^7\text{Li}$ and ${}^{31}\text{P}$ sites (see Appendix Tab. II). The different sites lead to positive and negative signs of the off diagonal elements A_{12} , A_{13} , A_{23} .

In Fig. 5 (a) the ${}^7\text{Li}$ -NMR spectrum shows a single resonance line in contrast to the ${}^{31}\text{P}$ -NMR spectrum in Fig. 5 (b) which shows two resonance lines for angles off $H_0||a$ and $H_0||c$. From comparison of the angle dependent ${}^{31}\text{P}$ -NMR data reported in¹⁴ and Fig. 5 (b) the crystal axes a and c are confirmed. For rotating between $H_0||c$

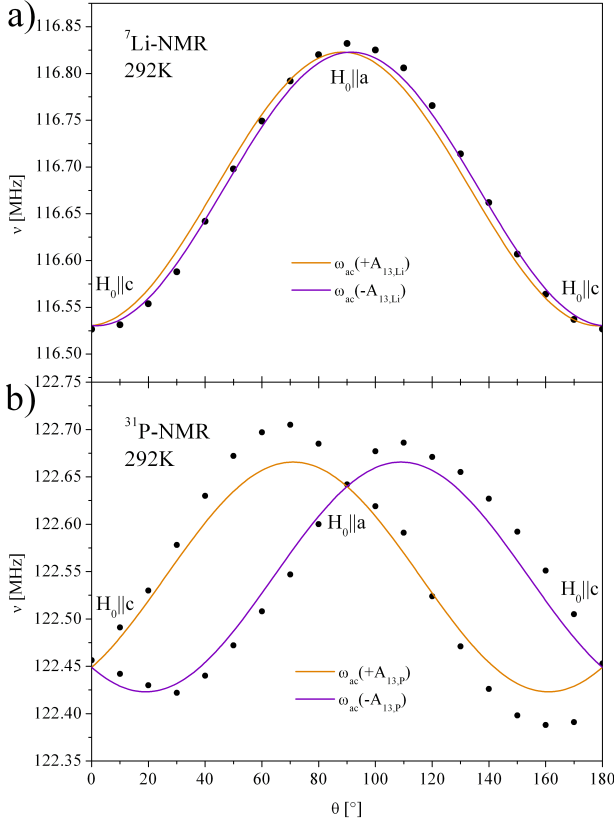


FIG. 5. Experimental orientation dependence of ^7Li - and ^{31}P -NMR between $H_0||c$ and $H_0||a$. Expected curves: $\nu_{ac} = \gamma_n H_0 (1 + (A_{11} \sin^2 \theta + 2A_{13} \sin \theta \cos \theta + A_{33} \cos^2 \theta) \chi(292K))$ for the corresponding ^7Li and ^{31}P tensor elements. The diagonal elements are experimental, A_{13} is calculated. a) The absolute value of $\pm A_{13,Li}$ is relatively small which leads to a small splitting of the ^7Li -NMR resonance line on the order of ~ 10 kHz which is not observable due to the broad resonance line of ~ 100 kHz. b) The line splitting of ~ 200 kHz is observable. The calculated off diagonal element $\pm A_{13,P}$ is ~ 10 times larger than $\pm A_{13,Li}$ which increases the splitting in the ^{31}P -NMR spectrum.

and $H_0||a$, Eqn. 3 simplifies to an equation which includes only the tensor elements A_{11} , A_{33} , A_{13} . The absolute value of A_{13} determines the size of splitting that means the difference between the violet and orange curve in Fig. 5. In the ^7Li -NMR spectra the $A_{13,Li}$ element leads to a splitting on the order of ~ 10 kHz which is completely covered by the broad linewidth of ~ 100 kHz. The value $A_{13,P}$ for ^{31}P is ~ 10 times larger than $A_{13,Li}$ (see Tab. I) and leads to a splitting of 200 kHz which can be nicely observed in the ^{31}P -NMR spectra. Fitting the experimental ^{31}P -NMR orientation dependent data in Fig. 5 (b) leads to experimental values for $A_{13,P}$ (see Appendix Tab. I).

The experimental results for rotating the crystal between $H_0||b$ and $H_0||a$ are shown in Fig. 6. For these orientations Eqn. 3 simplifies to an equation including only A_{11} , A_{22} and A_{12} . For this case A_{12} determines the

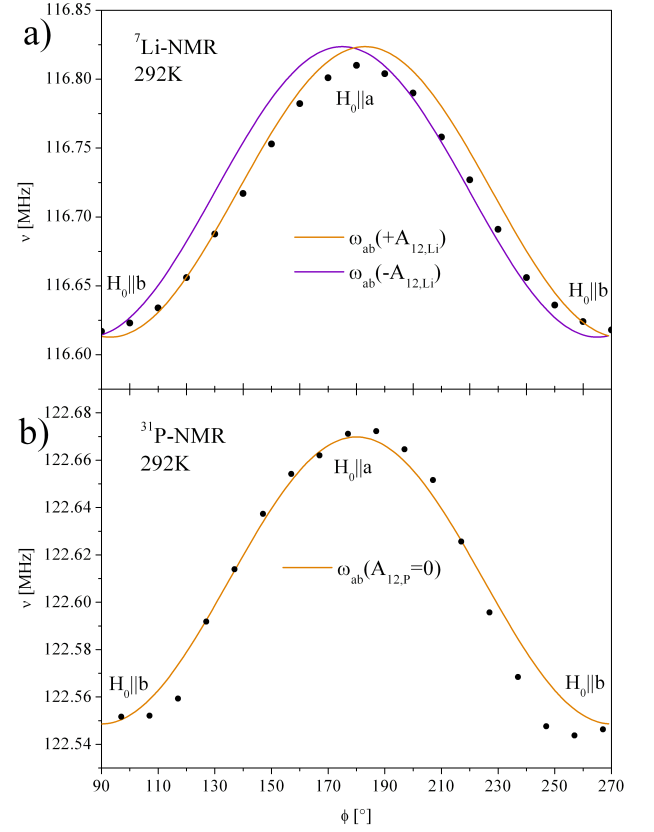


FIG. 6. Experimental orientation dependence of ^7Li - and ^{31}P -NMR between $H_0||b$ and $H_0||a$. Expected curves: $\nu_{ab} = \gamma_n H_0 (1 + (A_{11} \cos^2 \phi + 2A_{12} \sin \phi \cos \phi + A_{22} \sin^2 \phi) \chi(292K))$. a) $A_{12,Li}$ causes the splitting on the order of ~ 20 kHz which is too small to observe it by ^7Li -NMR because of the broad linewidth of ~ 100 kHz. b) $A_{12,P}$ vanishes (see Appendix Tab. I) which means that no splitting is present.

size of the splitting.

The orientation dependence between $H_0||b$ and $H_0||c$ is shown in Fig. 7. Here, Eqn. 3 includes only the tensor elements A_{22} , A_{33} and A_{23} . In this case the off diagonal element A_{23} is responsible for the splitting.

C. Discussion of the angle dependence

The angle dependence of the NMR spectra provides another indication that the broad lines and anomalous shape of the resonance lines in Fig. 2 are due to Mn disorder, and not due to differently oriented domains of the crystal. First of all, the angle dependencies of the ^7Li and the ^{31}P are completely different, but the shapes of the spectra are very similar. This can be seen in Fig. 5: whereas the ^{31}P lines split depending on the angle θ , the ^7Li lines do not. In contrast, the shape of the spectra for $H_0||a$ in Fig. 2 is very similar for both isotopes. An angle dependence as that of the ^{31}P in Fig. 5 (b) would clearly lead to a different shape of the spectrum compared to the ^7Li . Similar arguments hold for the other two directions.

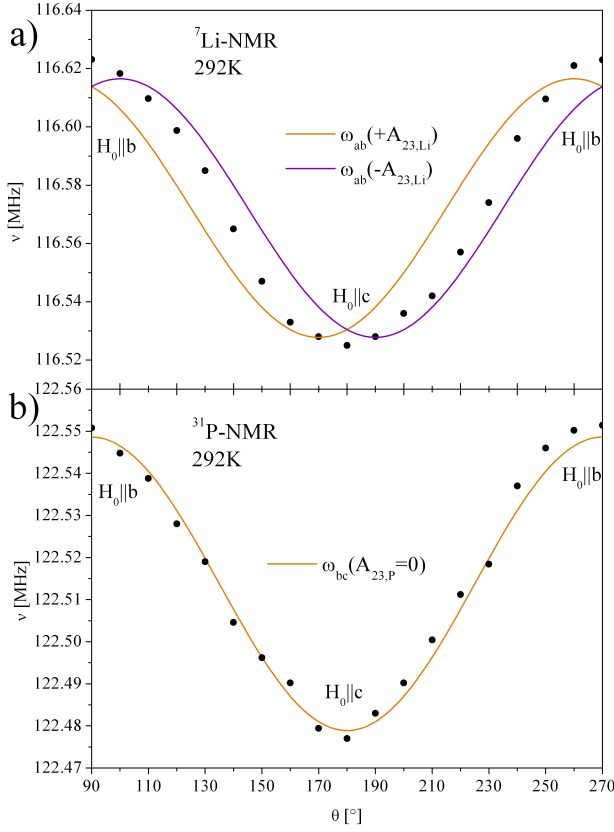


FIG. 7. Experimental orientation dependence of ${}^7\text{Li}$ - and ${}^{31}\text{P}$ -NMR between $H_0\|b$ and $H_0\|c$. Expected curves: $\nu_{bc} = \gamma_n H_0 (1 + (A_{22} \sin^2 \theta + 2A_{23} \sin \theta \cos \theta + A_{33} \cos^2 \theta) \chi(292\text{K}))$. a) $A_{23,\text{Li}}$ causes the splitting on the order of ~ 30 kHz which is too small to observe it by ${}^7\text{Li}$ -NMR because of the broad linewidth of ~ 100 kHz. b) $A_{23,\text{P}}$ vanishes (see Appendix Tab. I) which means that no splitting is present.

Especially for $H_0\|b$, the shape of the spectra for ${}^7\text{Li}$ and ${}^{31}\text{P}$ are very similar, but the angle dependencies in Fig. 6 and Fig. 7 are not. For example, in Fig. 6, the difference of the resonance frequency of the ${}^7\text{Li}$ for $H_0\|a$ and $H_0\|b$ is ~ 200 kHz, whereas it is only ~ 120 kHz for the ${}^{31}\text{P}$. In contrast, the distance between the shoulder and the peak for $H_0\|b$ in Fig. 2 is very similar for both isotopes, if not even larger for the ${}^{31}\text{P}$. The same argument is true for the linewidths in general: the angle dependent splitting is always larger for the ${}^7\text{Li}$, whereas the FWHM tends to be larger for the ${}^{31}\text{P}$. A broadening from differently oriented domains of a crystal would lead to the opposite trend, as can be deduced from the angle dependent measurements.

Furthermore, the comparison of the calculated and experimental tensor elements indicates the presence of an additional hyperfine interaction for the ${}^{31}\text{P}$ nuclei, whereas the values for the ${}^7\text{Li}$ in principle agree: the diagonal element $A_{11,\text{Li}}$ determined by NMR and the value determined from the crystal structure is the same, and the values for $A_{22,\text{Li}}$ and $A_{33,\text{Li}}$ are showing only a small residue. The difference can be explained by the asymmetric shape of the resonance line for $H_0\|b$ which is most

likely due to the Mn disorder. The calculation of the resonance frequency from the center of gravity therefore leads to a smaller shift of the resonance frequency than expected from the calculated $A_{22,\text{Li}}$. The residue of $A_{33,\text{Li}}$ possibly arises from the Mn disorder, too. Therefore, it can be concluded that the Mn disorder has its largest influence in b and c direction because of the larger discrepancies of $A_{22,\text{Li}}$ and $A_{33,\text{Li}}$ compared to $A_{11,\text{Li}}$. A small displacement of some of the Mn atoms from their original positions in the lattice leads to a distribution of the dipolar hyperfine couplings resulting in the broad lines and the asymmetric shape. Note that the off diagonal elements for ${}^7\text{Li}$ can in principle be determined, too. However, the splitting is only very small (~ 10 - 40 kHz), and therefore can not be resolved within the broad resonance lines (width ~ 100 kHz).

In contrast to the ${}^7\text{Li}$, the comparison of the experimental and calculated *diagonal* hyperfine coupling elements for the ${}^{31}\text{P}$ shows large residues (see Appendix Tab. I). Such a discrepancy has already been reported in¹⁴ and has been explained by non-dipolar hyperfine interactions of the ${}^{31}\text{P}$ nucleus with unpaired $3s$ (contact interaction) and/or $3p$ (core polarization) electrons of the phosphorous. These unpaired s and p electrons arise from the Mn-O-P-O-Mn superexchange path which is responsible for the interlayer magnetic coupling¹⁵. The difference between the experimental and calculated resonance frequencies of the ${}^{31}\text{P}$ -NMR corresponds to an isotropic difference in the diagonal elements of the hyperfine coupling tensor of $0.4 \text{ T}/\mu_B$ which underlines the isotropic character which is typical for a contact interaction.

The off diagonal element $A_{13,\text{P}}$ is causing a splitting of ~ 200 kHz for angles between $H_0\|a$ and $H_0\|c$ which is larger than the averaged linewidth and therefore observable by ${}^{31}\text{P}$ -NMR. From the obtained data the value of $A_{13,\text{P}}$ with positive and negative sign is extracted by fitting both angle dependent ${}^{31}\text{P}$ -NMR curves in Fig. 5 (b) by using Eqn. 3. The experimental absolute values of $\pm A_{13,\text{P}}$ are slightly larger. The deviations may arise from the Mn disorder.

D. NMR in the antiferromagnetic phase

In order to check the dipolar coupling and to investigate the influence of the spin flop on the NMR spectra, we measured the ${}^7\text{Li}$ - and ${}^{31}\text{P}$ spectra in the AFM phase at 4.2 K. In the single crystal at hand, the spin flop field at this temperature amounts to 3.9 T. The NMR spectra are shown in Fig. 8 (a) for the orientations $H_0\|a$, $H_0\|b$ and $H_0\|c$. In the AFM phase the bulk susceptibility can not be used to calculate the resonance frequencies from the dipolar hyperfine coupling, because a part of electron spins changes its orientation to the opposite direction. In zero external magnetic field, the electron spins align antiparallel along the crystallographic a -axis. For the NMR experiments, a strong external field $H_0 = 7 \text{ T}$ has been applied which leads to a tilt of the electron spins for the

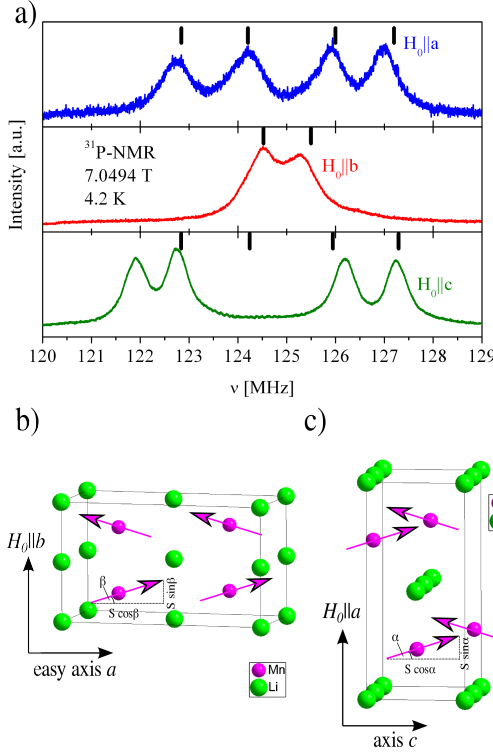


FIG. 8. a) ^{31}P -NMR spectra for $H_0 \parallel a$, $H_0 \parallel b$ and $H_0 \parallel c$ at 4.2 K. By assuming tilt angles, the ^{31}P -NMR frequencies can be calculated as shown in Tab. III. The best match of experimental and calculated frequencies is achieved for $\alpha = 11^\circ$, $\beta = 4^\circ$ and $\gamma = 13^\circ$. The calculated frequencies are indicated by the short black lines. b) Tilts of the electronic spins in the AFM state. Exemplified shown for tilts in b direction. For tilts in c direction (tilt angle γ) the situation is similar. c) Tilts in the SF state in the direction of a by the angle α . The tilt causes an additional component of the spins in field direction.

directions $H_0 \parallel b$ and $H_0 \parallel c$ by the angle β and γ , respectively, and to a spin-flop transition plus an additional tilt by the angle α for the direction $H_0 \parallel a$ (see Fig. 8 (b) and (c)). The occurrence of a spin-flop transition has been reported in^{10,20} for $H_0 > 4$ T parallel a . The tilt angle in the spin flop phase is labeled α .

Eqn. 4 considers the additional fields induced by the contact interaction B_c and the dipolar field $B_{\text{dip}}^{\text{AFM}}$ which stems from the antiferromagnetic order of the electron spins.

$$\nu = \gamma_n (H_0 + B_c + B_{\text{dip}}^{\text{AFM}}) \quad (4)$$

The dipolar field $B_{\text{dip,Li}}^{\text{AFM}}$ vanishes for the ^7Li sites in the AFM phase, therefore the ^7Li -NMR spectra show a single resonance line at the frequency of a bare nucleus. In Fig. 3 (a) the expected behavior is experimentally indicated by small shifts of the ^7Li -NMR resonance frequencies in the direction of the unshifted frequency at 4.2 K. The incomplete shifting to $\gamma_{\text{Li}} H_0$ can be explained by

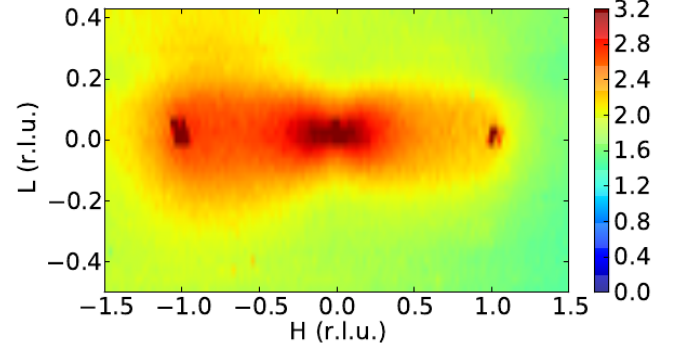


FIG. 9. Diffuse scattering intensity around the forbidden (030) position. The intensity is given in counts/second at 100 mA ring current.

a remaining dipolar field induced by the tilted electron spins.

The resonance lines in the AFM phase of the ^{31}P are shown in Fig. 8 (a) for the orientations $H_0 \parallel a$, $H_0 \parallel b$ and $H_0 \parallel c$. The number of resonance lines in the ^{31}P -NMR spectra equals the number of different calculated dipolar fields $B_{\text{dip,P}}^{\text{AFM}}$ (see Appendix Tab. III).

The additional component in the field direction due to the tilt of the electronic spins is considered in Tab. III for the corresponding orientations. Then, the ^{31}P NMR frequencies are calculated as a function of the tilt angles. The best match of experimental and calculated resonances are found for $\alpha = 11^\circ$, $\beta = 4^\circ$, and $\gamma = 13^\circ$. The calculated frequencies are indicated by bars in Fig. 8. For $H_0 \parallel a$ and $H_0 \parallel b$ the experimental and calculated resonance frequencies agree quite well, and the value for $H_0 \parallel a$ is also consistent with the tilt angle of 5.4° at $H_0 = 4.5$ T determined by neutron scattering¹⁰ since the tilt angle of the spins almost depend linearly on the field. Only for $H_0 \parallel c$, the calculated resonances on the low frequency side for some reason do not agree well with the experimental data.

In general, our results show that it is possible to determine the magnetic structure by NMR in the AFM phase, and even to determine the small tilt of the spins due to the applied magnetic field.

IV. DIFFUSE X-RAY DIFFRACTION

The NMR lineshape and angle dependence provide strong evidence for the presence of disorder of the Mn-sublattice. In order to verify this conclusion we performed diffuse HE-XRD experiments on the same single crystals studied by NMR. The HE-XRD experiments were performed using a photon energy of 100 keV. At these energies the penetration depth of the x-rays is of the order of millimeters, which guarantees the detection of true bulk properties and enables a direct comparison to the NMR results.

A representative data set is displayed in Fig. 9, where

the diffuse scattering around the symmetry forbidden (030) is displayed. The very broad and diffuse HE-XRD intensity in the HL-plane can clearly be observed. The strong diffuse scattering reveals significant structural disorder in the studied single crystals. The HE-XRD intensity is proportional to $(\mathbf{Q} \cdot \mathbf{d})^2$, where $\mathbf{Q}$ is the scattering vector and $\mathbf{d}$ represents the shift of a lattice site away from its ideal position. The diffuse scattering around $\mathbf{Q}=(0,3,0)$ therefore implies that the lattice disorder involves shifts parallel to the b -axis, which are only very weakly correlated along a . The distribution of the diffuse intensity is also very anisotropic within the (H3L)-plane, i.e., the underlying disorder is anisotropic in real space, consistent with the NMR results. The data in Fig. 9 further implies that the symmetry of the ideal lattice is not strictly fulfilled and therefore the symmetry forbidden $(\pm 1,3,0)$ and $(0,3,0)$ reflections are also observed. In addition to this the HE-XRD intensity is dominated by the shifts of the heavy elements in the lattice. The results in Fig. 9 therefore directly reveal the disorder in the Mn-sublattice and is in perfect agreement with the conclusions drawn from the NMR data.

Based on the available HE-XRD data, we cannot characterize the structural disorder in more detail. This is subject of ongoing investigations.

V. CONCLUSIONS

We presented angle and temperature dependent ^7Li - and ^{31}P -NMR and diffuse x-ray diffraction measurements in a LiMnPO_4 single crystal. The ^7Li - and ^{31}P -NMR resonance lines in the AFM and SF phase are consistent with the calculated resonances, when tilts of the magnetic moments in the direction of the external field are assumed. The broad ^7Li - and ^{31}P -NMR resonance lines in the paramagnetic phase indicate the existence of Mn site disorder. In combination with the susceptibility data the diagonal elements of the hyperfine coupling tensor are determined and compared with the values calculated from the crystal structure. The highest deviations show $A_{22,\text{Li}}$ and $A_{33,\text{Li}}$ which leads to the conclusion that the Mn disorder exists predominantly in b and c direction. This is fully consistent with our HE-XRD data which indicates substantial-Mn disorder along the b direction. Interestingly, recent theoretical results imply a strong coupling of the Li- and the Mn-sublattice in the fully lithiated limit⁵. The Mn-disorder may hence be caused by the distribution of the mobile Li-ions within the MnPO_4 host. Our finding of Mn disorder in LiMnPO_4 therefore provides experimental evidence that the movement of Li within LiMnPO_4 is significantly coupled to lattice distortions. Certainly, this will affect also the mobility of the Li in LiMnPO_4 , and therefore the performance of this material as a battery.

ACKNOWLEDGMENTS

This research was financially supported by the DFG priority program SPP1473 (Grant No. GR3330/3-1 and KL1824/5). N.W. and R.K. acknowledge support by the BMBF via project 03SF0397. J.G. and S.P. gratefully acknowledge the financial support by the German Research Foundation through the Emmy-Noether program (Grant No. GE1647/2-1).

APPENDIX: CALCULATED AND EXPERIMENTAL HYPERFINE COUPLINGS

TABLE I. Comparison of calculated and NMR determined tensor elements for the paramagnetic phase. The elements for the AFM phase are calculated. All elements are given in T/ μ_B .

Nuclei	Tensor Element	Paramagnetic phase			AFM phase Crystal structure (calculated)
		Crystal structure (calculated)	NMR (experimental)	Residue	
^7Li	$A_{11,\text{Li}}$	0.0690	0.0717	0.0027	0
	$A_{22,\text{Li}}$	-0.0401	-0.0198	0.0203	0
	$A_{33,\text{Li}}$	-0.0289	-0.0430	-0.0141	0
	$A_{12,\text{Li}}$	± 0.0058	-	-	0
	$A_{13,\text{Li}}$	± 0.0030	-	-	0
	$A_{23,\text{Li}}$	± 0.0060	-	-	0
^{31}P	$A_{11,\text{P}}$	0.0376	0.4429	0.4053	± 0.0881
	$A_{22,\text{P}}$	-0.0193	0.3847	0.4040	± 0.1560
	$A_{33,\text{P}}$	-0.0183	0.3710	0.3893	± 0.0679
	$A_{12,\text{P}}$	0	-	-	0
	$A_{13,\text{P}}$	± 0.0282	$+0.0388 / -0.0362$	$0.0106 / 0.0080$	± 0.0374
	$A_{23,\text{P}}$	0	-	-	0

TABLE II. The signs for the off diagonal elements of the magnetic unequal ^7Li and ^{31}P sites are shown. The sites are given in fractional coordinates.

^7Li sites	$A_{12,\text{Li}}$	$A_{13,\text{Li}}$	$A_{23,\text{Li}}$	^{31}P sites	$A_{13,\text{P}}$
(0 / 0 / 0)	+	+	-	(0.907 / 0.75 / 0.591)	-
(0 / 0.5 / 0)	-	+	+	(0.092 / 0.25 / 0.408)	-
(0.5 / 0 / 0.5)	+	-	+	(0.407 / 0.75 / 0.906)	+
(0.5 / 0.5 / 0.5)	-	-	-	(0.592 / 0.25 / 0.094)	+

TABLE III. The mathematical description for the orientations of $\vec{I}$ and $\vec{S}_j^T$ in the AFM phase is given in the second column. The result is shown in the third column. The number of different $B_{\text{dip,P}}^{\text{AFM}}$ is obtained from the combination possibilities of the $\pm$ sign of the tensor elements in the third column. The number of different dipolar fields $B_{\text{dip,P}}^{\text{AFM}}$ equals the number of experimental ^{31}P -NMR resonance lines. The tilt angles α, β, γ are defined in Fig. 8 (b) and (c).

	$\vec{I}$	$\hat{A}_{\text{dip,P}}^{\text{AFM}}$	$\cdot \vec{S}^T$	$B_{\text{dip,P}}^{\text{AFM}} \propto \sum_j (\vec{I} \cdot \hat{A}_{j,\text{P}}^{\text{AFM}} \cdot \vec{S}_j^T)$	Number of different $B_{\text{dip,P}}^{\text{AFM}}$
$H_0 \parallel a$	$\begin{pmatrix} \frac{1}{2} \\ 0 \\ 0 \end{pmatrix}$	$\begin{pmatrix} \pm A_{11} & 0 & \pm A_{13} \\ 0 & \pm A_{22} & 0 \\ \pm A_{13} & 0 & \pm A_{33} \end{pmatrix}$	$\frac{5}{2} \begin{pmatrix} \sin \alpha \\ 0 \\ \cos \alpha \end{pmatrix}$	$\frac{5}{4} [(\pm A_{11}) \sin \alpha + (\pm A_{13}) \cos \alpha]$	4
$H_0 \parallel b$	$\begin{pmatrix} 0 \\ \frac{1}{2} \\ 0 \end{pmatrix}$	$\begin{pmatrix} \pm A_{11} & 0 & \pm A_{13} \\ 0 & \pm A_{22} & 0 \\ \pm A_{13} & 0 & \pm A_{33} \end{pmatrix}$	$\frac{5}{2} \begin{pmatrix} \cos \beta \\ \sin \beta \\ 0 \end{pmatrix}$	$\frac{5}{4} (\pm A_{22}) \sin \beta$	2
$H_0 \parallel c$	$\begin{pmatrix} 0 \\ 0 \\ \frac{1}{2} \end{pmatrix}$	$\begin{pmatrix} \pm A_{11} & 0 & \pm A_{13} \\ 0 & \pm A_{22} & 0 \\ \pm A_{13} & 0 & \pm A_{33} \end{pmatrix}$	$\frac{5}{2} \begin{pmatrix} \cos \gamma \\ 0 \\ \sin \gamma \end{pmatrix}$	$\frac{5}{4} [(\pm A_{13}) \cos \gamma + (\pm A_{33}) \sin \gamma]$	4

-
- ¹ A. K. Padhi, K. S. Najundaswamy, and J. B. Goodenough, *J. Electrochem. Soc.* **144** (1997).
 - ² Z. Nie, C. Ouyang, J. Chen, Z. Zhong, Y. Du, D. Liu, S. Shi, and M. Lei, *Solid State Communications* **150**, 40 (2010).
 - ³ S. K. Martha, B. Markovsky, J. Grinblat, Y. Gofer, O. Haik, E. Zinigrad, D. Aurbach, T. Drezen, D. Wang, G. Deghenghi, and I. Exnar, *J. Electrochem. Soc.* **156**, A541 (2009).
 - ⁴ G. Li, H. Azuma, and M. Tohda, *Electrochemical and Solid-State Letters*, A135 (2002).
 - ⁵ Y. Asari, Y. Suwa, and T. Hamada, *Phys. Rev. B* **84**, 134113 (2011).
 - ⁶ A. Yamada and S. Chung, *J. Electrochem. Soc.* **148**, A960 (2001).
 - ⁷ A. Yamada, Y. Kudo, and K. Liu, *J. Electrochem. Soc.* **148**, A1153 (2001).
 - ⁸ D. Wang, H. Buqa, M. Crouzet, G. Deghenghi, T. Drezen, I. Exnar, N.-H. Kwon, J. H. Miners, L. Poletto, and M. Grätzel, *Journal of Power Sources* **189**, 624 (2009).
 - ⁹ V. Aravindan, J. Gnanaraj, Y.-S. Lee, and S. Madhavi, *J. Mater. Chem. A* **1**, 3518 (2013).
 - ¹⁰ R. Toft-Petersen, N. H. Andersen, H. Li, J. Li, W. Tian, S. L. Bud'ko, T. B. S. Jensen, C. Niedermayer, M. Laver, O. Zaharko, J. W. Lynn, and D. Vaknin, *Phys. Rev. B* **85**, 224415 (2012).
 - ¹¹ B. B. Van Aken, J.-P. Rivera, H. Schmid, and M. Fiebig, *NATURE* **449**, 702 (2007).
 - ¹² N. Wizen, G. Behr, F. Lipps, I. Hellmann, R. Klingeler, V. Kataev, W. Löser, N. Sato, and B. Büchner, *Journal of Crystal Growth* **311**, 1273 (2009).
 - ¹³ N. Wizen, G. Behr, W. Löser, B. Büchner, and R. Klingeler, *Journal of Crystal Growth* **318**, 995 (2011).
 - ¹⁴ J. M. Mays, *Physical Review* **131** (1963).
 - ¹⁵ J. Li, W. Tian, Y. Chen, J. L. Zarestky, J. W. Lynn, and D. Vaknin, *Phys. Rev. B* **79**, 144410 (2009).
 - ¹⁶ P. Heitjans and J. Kärger, *Diffusion in Condensed Matter - Methods, Materials, Models* (Springer, 2005).
 - ¹⁷ K. Nakamura, H. Ohno, K. Okamura, Y. Michihiro, T. Moriga, I. Nakabayashi, and T. Kanashiro, *Solid State Ionics* **177**, 821 (2006).
 - ¹⁸ A. Abragam, *The Principles of Nuclear Magnetism* (Clarendon Press, Oxford, 1961).
 - ¹⁹ D. Arcon, A. Zorko, R. Dominko, and Z. Jaglicic, *J. Phys. Condensed Matter* **16**, 5531 (2004).
 - ²⁰ H. J. Ranicar and P. R. Elliston, *Physics Letters* **25A** (1967).